


Manufacturer address	James Walker Moorflex Ltd, John Escritt Road, BD16 2BS West Yorkshire, GB	According to EN 13555 2021-4
Product name	Fluolion® 800	
Product dimensions	92 x 49 x 2 mm	

Minimum stress to seal $Q_{min(L)}$ (at assembly), $Q_{smin(L)}$ (after off-loading) for $p = 10 \text{ bar}$ ($T = 23 \pm 2 \text{ }^\circ\text{C}$)											
L [mg/(s·m)]	$Q_{min(L)}$ [MPa]	$Q_{smin(L)}$ [MPa]									
		$Q_A = 10$ [MPa]	$Q_A = 15$ [MPa]	$Q_A = 20$ [MPa]	$Q_A = 30$ [MPa]	$Q_A = 40$ [MPa]	$Q_A = 60$ [MPa]	$Q_A = 80$ [MPa]	$Q_A = 100$ [MPa]	$Q_A = 161$ [MPa]	
1E-0	10		5	5	5	5	5	5	5	5	5
1E-1	10		5	5	5	5	5	5	5	5	5
1E-2	10		5	5	5	5	5	5	5	5	5
1E-3	16			7	5	5	5	5	5	5	5
1E-4	21				5	5	5	5	5	5	5
1E-5	26				10	6	7	6	7	5	5
1E-6	87									58	43
1E-7											



Minimum stress to seal $Q_{min(L)}$ (at assembly), $Q_{smin(L)}$ (after off-loading) for $p = 40 \text{ bar}$ ($T = 23 \pm 2 \text{ }^\circ\text{C}$)											
L [mg/(s·m)]	$Q_{min(L)}$ [MPa]	$Q_{smin(L)}$ [MPa]									
		$Q_A = 10$ [MPa]	$Q_A = 20$ [MPa]	$Q_A = 40$ [MPa]	$Q_A = 60$ [MPa]	$Q_A = 80$ [MPa]	$Q_A = 100$ [MPa]	$Q_A = 120$ [MPa]	$Q_A = 140$ [MPa]	$Q_A = 160$ [MPa]	
1E-0	10		10	10	10	10	10	10			10
1E-1	14		10	10	10	10	10	10			10
1E-2	19		10	10	10	10	10	10			10
1E-3	29			10	10	10	10	10			10
1E-4	40				35	10	10	10			10
1E-5	67						23	16			15
1E-6											
1E-7											

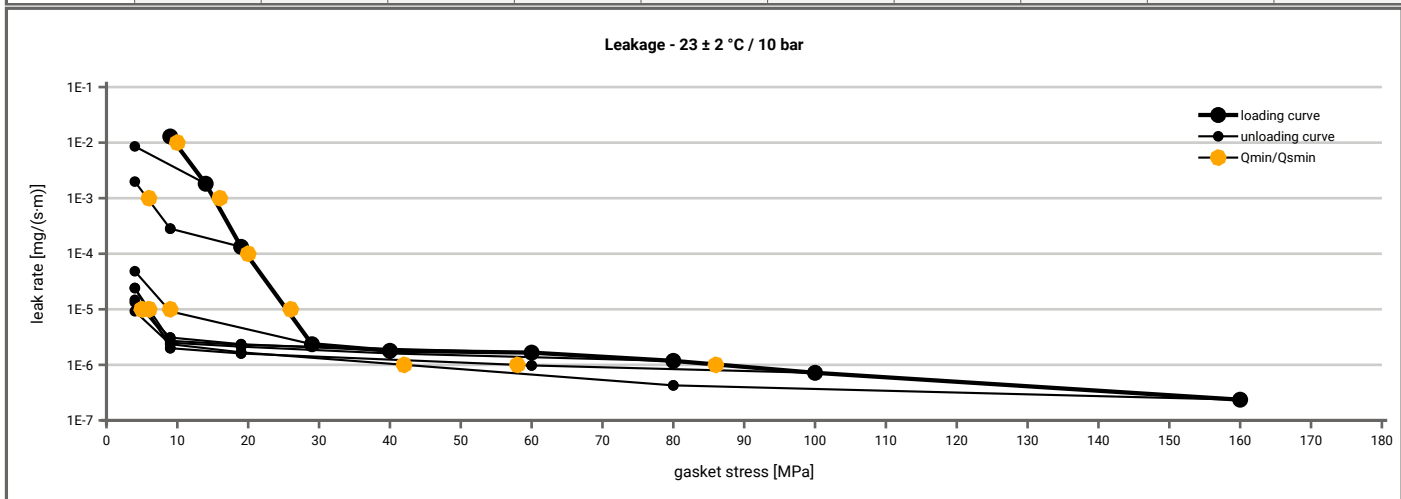