



Manufacturer address	James Walker Moorflex Ltd, John Escritt Road, BD16 2BS West Yorkshire, GB	According to EN 13555 2021-4
Product name	Fluolion® 900	
Product dimensions	92 x 49 x 2 mm	

Minimum stress to seal $Q_{min(L)}$ (at assembly), $Q_{smin(L)}$ (after off-loading) for $p = 10$ bar ($T = 23 \pm 2$ °C)									
L [mg/(s·m)]	$Q_{min(L)}$ [MPa]	$Q_{smin(L)}$ [MPa]							
		$Q_A = 10$ [MPa]	$Q_A = 15$ [MPa]	$Q_A = 20$ [MPa]	$Q_A = 30$ [MPa]	$Q_A = 40$ [MPa]	$Q_A = 60$ [MPa]	$Q_A = 80$ [MPa]	$Q_A = 100$ [MPa]
1E-0	10			10	10	10	10	10	10
1E-1	10			10	10	10	10	10	10
1E-2	11			10	10	10	10	10	10
1E-3	16			10	10	10	10	10	10
1E-4	22				10	10	10	10	10
1E-5	29				22	10	10	10	10
1E-6									
1E-7									

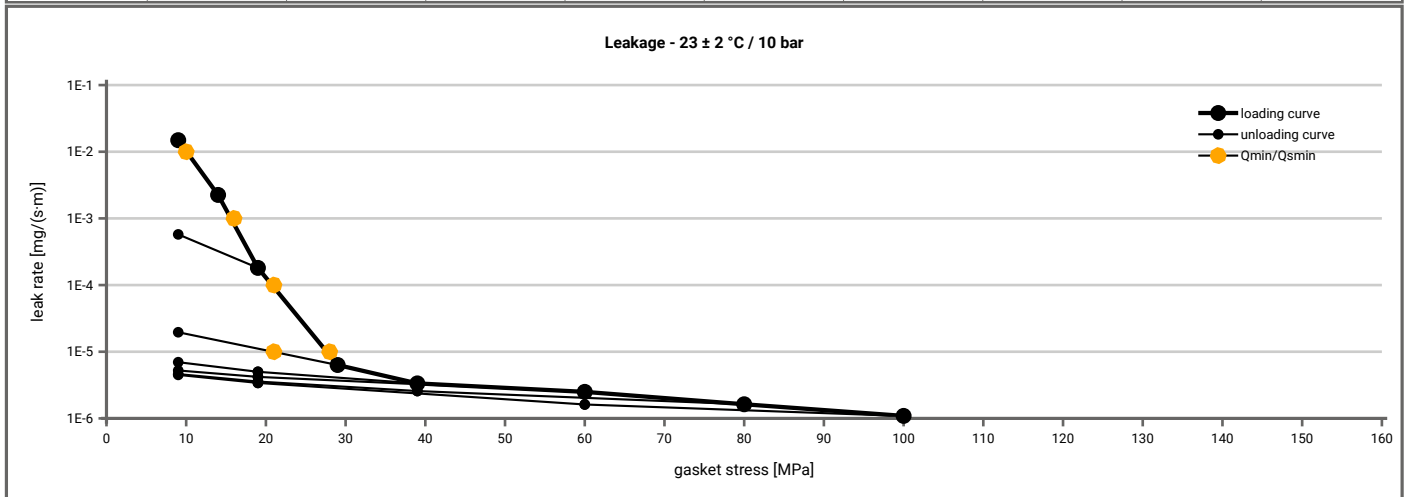

Minimum stress to seal $Q_{min(L)}$ (at assembly), $Q_{smin(L)}$ (after off-loading) for $p = 40$ bar ($T = 23 \pm 2$ °C)									
L [mg/(s·m)]	$Q_{min(L)}$ [MPa]	$Q_{smin(L)}$ [MPa]							
		$Q_A = 10$ [MPa]	$Q_A = 15$ [MPa]	$Q_A = 20$ [MPa]	$Q_A = 30$ [MPa]	$Q_A = 40$ [MPa]	$Q_A = 60$ [MPa]	$Q_A = 80$ [MPa]	$Q_A = 100$ [MPa]
1E-0	10			10	10	10	10	10	10
1E-1	15			10	10	10	10	10	10
1E-2	19			16	10	10	10	10	10
1E-3	24				10	10	10	10	10
1E-4	28				19	10	10	10	10
1E-5	97								51
1E-6									
1E-7									

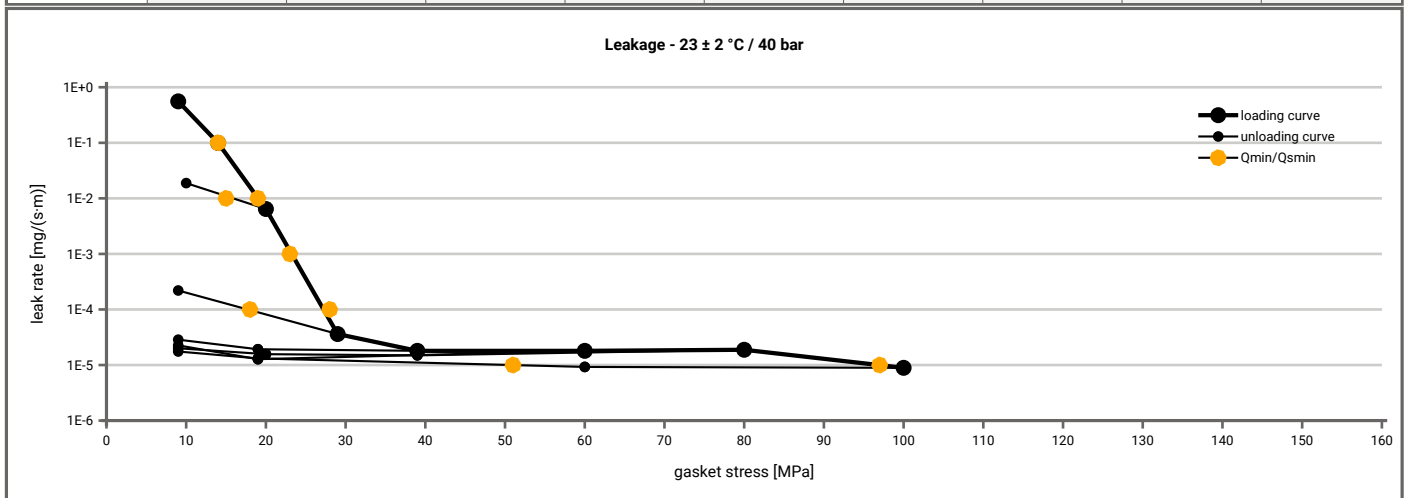

Manufacturer address	James Walker Moorflex Ltd, John Escritt Road, BD16 2BS West Yorkshire, GB	According to EN 13555 2021-4
Product name	Fluolion® 900	
Product dimensions	92 x 49 x 2 mm	

Minimum stress to seal $Q_{min(L)}$ (at assembly), $Q_{smin(L)}$ (after off-loading) for $p = 63 \text{ bar}$ ($T = 23 \pm 2 \text{ }^\circ\text{C}$)								
L [mg/(s·m)]	$Q_{min(L)}$ [MPa]	$Q_{smin(L)}$ [MPa]						
		$Q_A = 10$ [MPa]	$Q_A = 20$ [MPa]	$Q_A = 30$ [MPa]	$Q_A = 40$ [MPa]	$Q_A = 60$ [MPa]	$Q_A = 80$ [MPa]	$Q_A = 100$ [MPa]
1E-0	10		10	10	10	10	10	10
1E-1	14		10	10	10	10	10	10
1E-2	19		15	10	10	10	10	10
1E-3	24			14	10	10	10	10
1E-4	30			30	13	10	10	10
1E-5	88							51
1E-6								
1E-7								

