



|                             |   |  |
|-----------------------------|---|--|
| <b>Manufacturer address</b> | Kempchen Dichtungstechnik GmbH, Im Waldteich 21, 46147 Oberhausen, DE | According to<br><b>DIN EN 13555</b><br><b>2005-2</b> |
| <b>Product name</b>         | Rivatherm Super A1 RS2E2-S (1.4401; 98%, D = 1,0g/ccm)                |  |
| <b>Product dimensions</b>   | 92 x 49 x 2 mm (DIN EN 1514-1 1997-8)                                 |  |

| Minimum stress to seal $Q_{min(L)}$ (at assembly), $Q_{smin(L)}$ (after off-loading) for $p = 10$ bar ( $T = 23 \pm 2$ °C) |                    |                     |                  |                  |                  |                  |                  |                   |
|--|--------------------|---------------------|------------------|------------------|------------------|------------------|------------------|-------------------|
| L [mg/(s·m)]   | $Q_{min(L)}$ [MPa] | $Q_{smin(L)}$ [MPa] |                  |                  |                  |                  |                  |                   |
|  |                    | $Q_A = 5.2$ [MPa]   | $Q_A = 10$ [MPa] | $Q_A = 20$ [MPa] | $Q_A = 40$ [MPa] | $Q_A = 60$ [MPa] | $Q_A = 80$ [MPa] | $Q_A = 100$ [MPa] |
| 1E-0   | 5                  |                     | 5                | 5                | 5                | 5                | 5                | 5                 |
| 1E-1   | 5                  |                     | 5                | 5                | 5                | 5                | 5                | 5                 |
| 1E-2   | 9                  |                     | 7                | 5                | 5                | 5                | 5                | 5                 |
| 1E-3   | 37                 |                     |                  |                  | 31               | 14               | 5                | 5                 |
| 1E-4   | 67                 |                     |                  |                  |                  |                  | 50               | 36                |
| 1E-5   |                    |                     |                  |                  |                  |                  |                  |                   |
| 1E-6   |                    |                     |                  |                  |                  |                  |                  |                   |
| 1E-7   |                    |                     |                  |                  |                  |                  |                  |                   |
| 1E-8   |                    |                     |                  |                  |                  |                  |                  |                   |

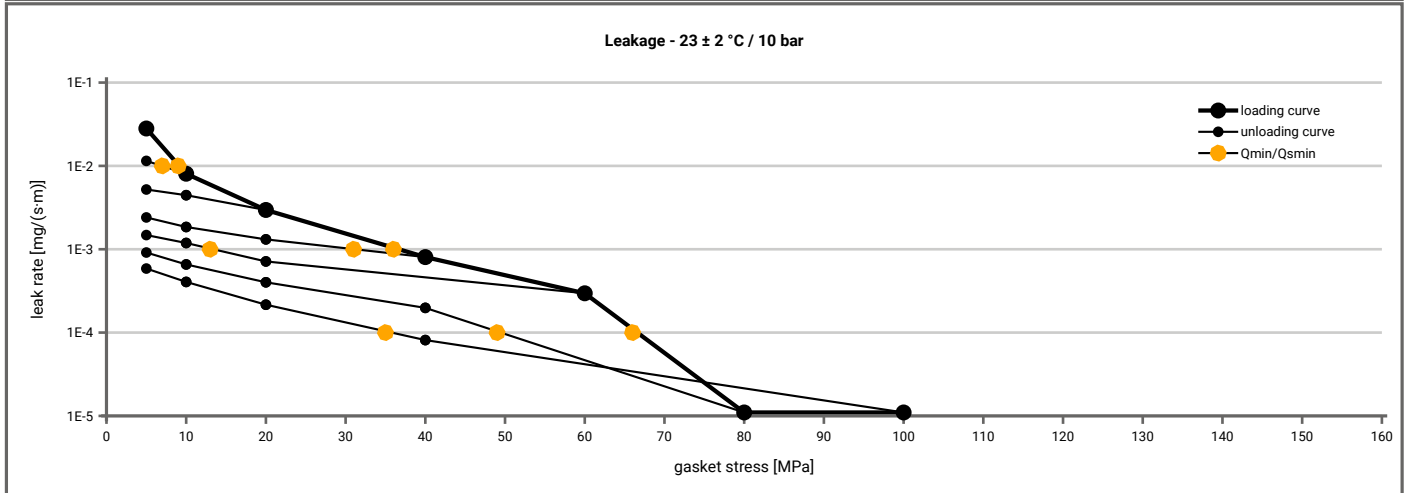

| Minimum stress to seal $Q_{min(L)}$ (at assembly), $Q_{smin(L)}$ (after off-loading) for $p = 40$ bar ( $T = 23 \pm 2$ °C) |                    |                     |                  |                  |                  |                  |                   |
|--|--------------------|---------------------|------------------|------------------|------------------|------------------|-------------------|
| L [mg/(s·m)]   | $Q_{min(L)}$ [MPa] | $Q_{smin(L)}$ [MPa] |                  |                  |                  |                  |                   |
|  |                    | $Q_A = 10$ [MPa]    | $Q_A = 20$ [MPa] | $Q_A = 40$ [MPa] | $Q_A = 60$ [MPa] | $Q_A = 80$ [MPa] | $Q_A = 100$ [MPa] |
| 1E-0   | 10                 |                     | 10               | 10               | 10               | 10               | 10                |
| 1E-1   | 10                 |                     | 10               | 10               | 10               | 10               | 10                |
| 1E-2   | 25                 |                     |                  | 10               | 10               | 10               | 10                |
| 1E-3   | 62                 |                     |                  |                  |                  | 39               | 21                |
| 1E-4   | 86                 |                     |                  |                  |                  |                  | 64                |
| 1E-5   |                    |                     |                  |                  |                  |                  |                   |
| 1E-6   |                    |                     |                  |                  |                  |                  |                   |
| 1E-7   |                    |                     |                  |                  |                  |                  |                   |
| 1E-8   |                    |                     |                  |                  |                  |                  |                   |

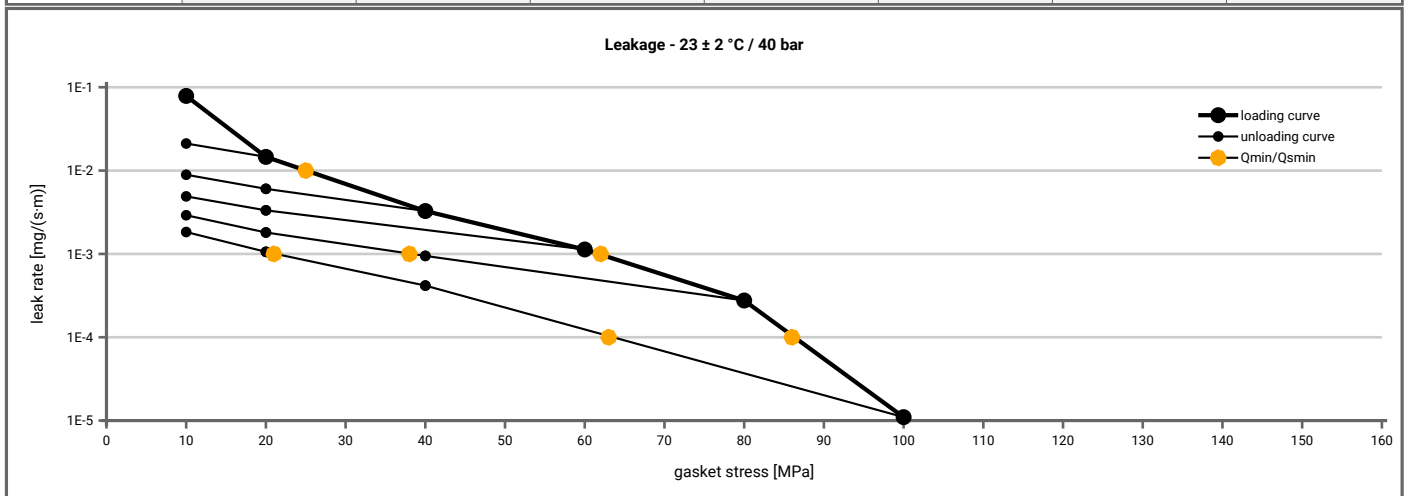

Note: the content of darkened cells was not determined respectively is unnecessary Rev.-No.: 1 Creation date of this sheet: 2013-01-23

|                             |   |  |
|-----------------------------|---|--|
| <b>Manufacturer address</b> | Kempchen Dichtungstechnik GmbH, Im Waldteich 21, 46147 Oberhausen, DE | According to<br><b>DIN EN 13555</b><br><b>2005-2</b> |
| <b>Product name</b>         | Rivatherm Super A1 RS2E2-S (1.4401; 98%, D = 1,0g/ccm)                |  |
| <b>Product dimensions</b>   | 92 x 49 x 2 mm (DIN EN 1514-1 1997-8)                                 |  |

| Relaxation ratio $P_{QR}$ for stiffness $C = 500$ [kN/mm]                      |           |                      |                        |                      |                        |                      |                        |                      |          |                      |
|--|-----------|----------------------|------------------------|----------------------|------------------------|----------------------|------------------------|----------------------|----------|----------------------|
| Gasket stress  | 23 ± 2 °C |                      | Temperature 1 [100 °C] |                      | Temperature 2 [200 °C] |                      | Temperature 3 [300 °C] |                      | $P_{QR}$ | $\Delta e_{Gc}$ [µm] |
|  | $P_{QR}$  | $\Delta e_{Gc}$ [µm] | $P_{QR}$               | $\Delta e_{Gc}$ [µm] | $P_{QR}$               | $\Delta e_{Gc}$ [µm] | $P_{QR}$               | $\Delta e_{Gc}$ [µm] |          |                      |
| Stress level 1 [30 MPa]  | 0.98      | 6                    | 0.94                   | 16                   | 0.88                   | 31                   | 0.99                   | 4                    |          |                      |
| Stress level 2 [50 MPa]  | 0.99      | 6                    | 0.96                   | 17                   | 0.93                   | 29                   | 0.94                   | 25                   |          |                      |
|  |           |                      |                        |                      |                        |                      |                        |                      |          |                      |
|  |           |                      |                        |                      |                        |                      |                        |                      |          |                      |
|  |           |                      |                        |                      |                        |                      |                        |                      |          |                      |
|  |           |                      |                        |                      |                        |                      |                        |                      |          |                      |
|  |           |                      |                        |                      |                        |                      |                        |                      |          |                      |
|  |           |                      |                        |                      |                        |                      |                        |                      |          |                      |
| $P_{QR}$ and $\Delta e_{Gc}$ at maximum gasket stress to be applied $Q_{smax}$ |           |                      |                        |                      |                        |                      |                        |                      |          |                      |
| $P_{QR}$ at $Q_{smax}$   | 1.00      | 8                    | 0.97                   | 45                   | 0.83                   | 235                  | 0.78                   | 227                  |          |                      |
| $Q_{smax}$   | 180 MPa   |                      | 180 MPa                |                      | 160 MPa                |                      | 120 MPa                |                      |          |                      |

| Sekant unloading modulus of the gasket $E_G$ [MPa] and gasket thickness $e_G$ [mm] |             |            |                        |            |                        |            |                        |            |             |            |
|--|-------------|------------|------------------------|------------|------------------------|------------|------------------------|------------|-------------|------------|
| Gasket stress [MPa]  | 23 ± 2 °C   |            | Temperature 1 [100 °C] |            | Temperature 2 [200 °C] |            | Temperature 3 [300 °C] |            | $E_G$ [MPa] | $e_G$ [mm] |
|  | $E_G$ [MPa] | $e_G$ [mm] | $E_G$ [MPa]            | $e_G$ [mm] | $E_G$ [MPa]            | $e_G$ [mm] | $E_G$ [MPa]            | $e_G$ [mm] |             |            |
| 0  | 0           | 1.976      | 0                      | 1.844      | 0                      | 1.958      | 0                      | 1.830      |             |            |
| 1  | 0           | 1.976      | 0                      | 1.844      | 0                      | 1.958      | 0                      | 1.830      |             |            |
| 20   | 473         | 1.385      | 577                    | 1.299      | 509                    | 1.514      | 462                    | 1.533      |             |            |
| 30   | 805         | 1.308      | 952                    | 1.237      | 688                    | 1.462      | 736                    | 1.490      |             |            |
| 40   | 1209        | 1.265      | 1109                   | 1.193      | 1000                   | 1.422      | 1310                   | 1.454      |             |            |
| 50   | 1354        | 1.232      | 1337                   | 1.162      | 1391                   | 1.393      | 1433                   | 1.424      |             |            |
| 60   | 1801        | 1.207      | 1980                   | 1.141      | 1494                   | 1.371      | 1627                   | 1.400      |             |            |
| 80   | 2197        | 1.165      | 2029                   | 1.101      | 1785                   | 1.332      | 3379                   | 1.371      |             |            |
| 100  | 3026        | 1.141      | 3011                   | 1.076      | 2723                   | 1.307      | 2422                   | 1.342      |             |            |
| 120  | 4206        | 1.122      | 3865                   | 1.059      | 3458                   | 1.181      | 2547                   | 1.319      |             |            |
| 140  | 4466        | 1.104      | 4780                   | 1.044      | 3832                   | 1.093      |                        |            |             |            |
| 160  | 4437        | 1.090      | 4751                   | 1.028      | 3394                   | 1.026      |                        |            |             |            |
| 180  | 4845        | 1.078      | 5195                   | 1.007      |                        |            |                        |            |             |            |

