



Company Address	W. L. Gore & Associates GmbH, Hermann-Oberth-Strasse 22, 85640 Putzbrunn, Germany	According to DIN EN 13555 2014-07
Gasket Type	GORE® GR Sheet Gasketing	
Sealing element dimensions [mm]	92 x 49 x 3	

L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 10 bar												
		Q _{Smin/L} [MPa]												
		Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa								
10 ⁰	10	10	10	10	10	10								
10 ⁻¹	12	10	10	10	10	10								
10 ⁻²	26		10	10	10	10								
10 ⁻³	39			37	10	10								
10 ⁻⁴	49				10	10								
10 ⁻⁵	59				10	10								

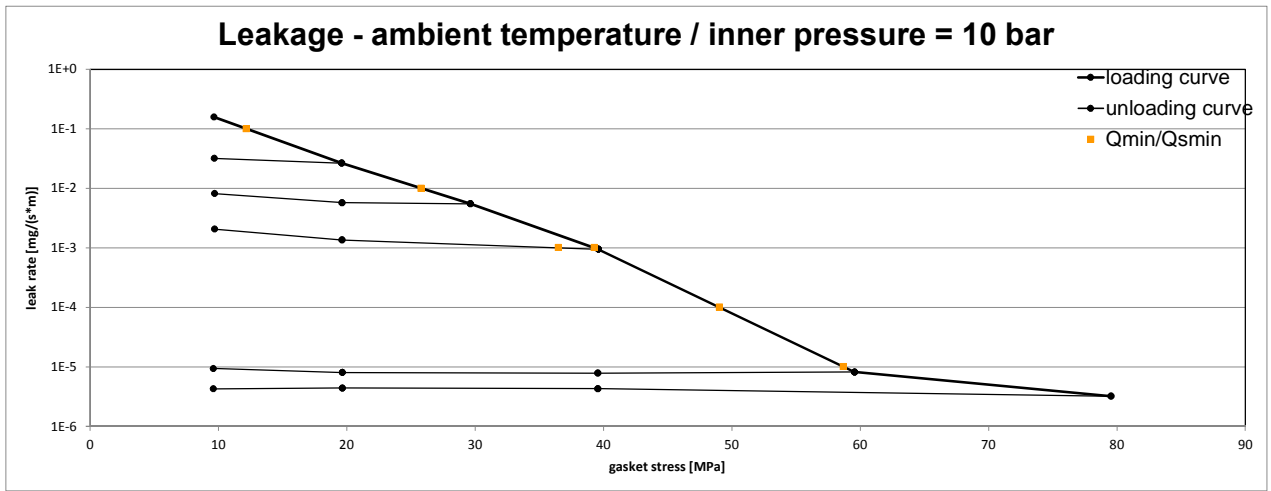


L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 20 bar												
		Q _{Smin/L} [MPa]												
		Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa								
10 ⁰	10	10	10	10	10	10								
10 ⁻¹	17		10	10	10	10								
10 ⁻²	30			10	10	10								
10 ⁻³	42				10	10								
10 ⁻⁴	52				10	10								
10 ⁻⁵	70					10								

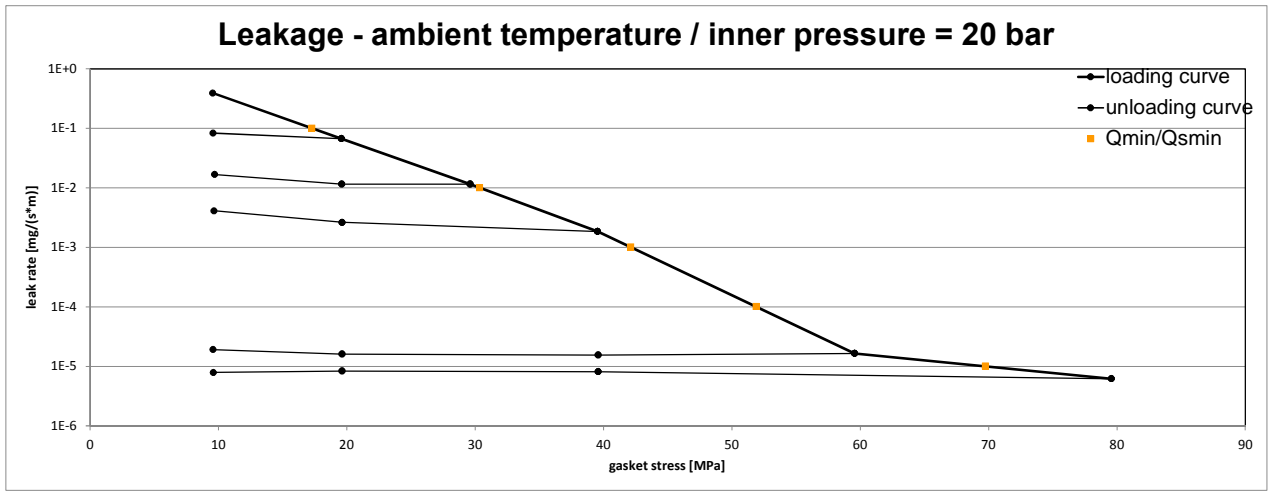

Note: the content of darkened cells was not determined respectively is unnecessary Rev - No: 2 Creation date of this sheet: 2016-01-25

Company Address	W. L. Gore & Associates GmbH, Hermann-Oberth-Strasse 22, 85640 Putzbrunn, Germany	According to DIN EN 13555 2014-07
Gasket Type	GORE® GR Sheet Gasketing	
Sealing element dimensions [mm]	92 x 49 x 3	

L [mg/(s*m)]	Q _{min,L} [MPa]	Minimum stress to seal Q _{min,L} (at assembly), Q _{Smin,L} (after off-loading) for p = 40 bar					Q _{Smin,L} [MPa]				
		Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa					
10 ⁰	11	10	10	10	10	10					
10 ⁻¹	24		10	10	10	10					
10 ⁻²	37			14	10	10					
10 ⁻³	47				10	10					
10 ⁻⁴	56										

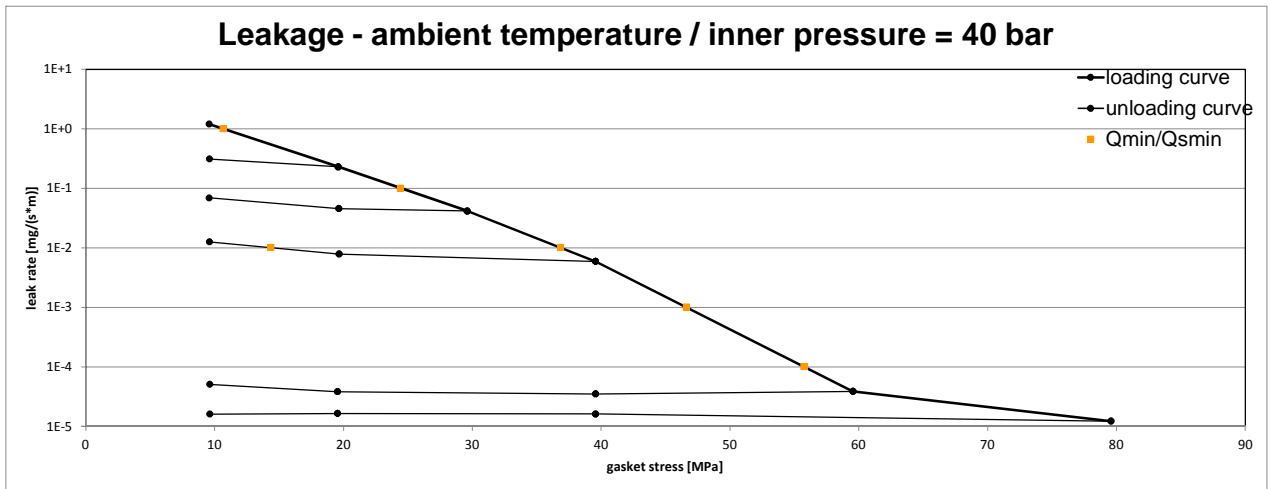

Note: the content of darkened cells was not determined respectively is unnecessary Rev - No: 2 Creation date of this sheet: 2016-01-25

