


Company Address	Teadit International Produktions GmbH, Rosenheimerstraße 10, 6330 Kufstein, Austria
Gasket Type	28LS-LE
Sealing element dimensions [mm]	92 x 49 x 3

L [mg/(s*m)]	Q _{min/L} [MPa]	Minimum stress to seal Q _{min/L} (at assembly), Q _{Smin/L} (after off-loading) for p = 40 bar					Q _{Smin/L} [MPa]				
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa					
10 ⁰	5	5	5	5	5	5					
10 ⁻¹	5	5	5	5	5	5					
10 ⁻²	5	5	5	5	5	5					
10 ⁻³	8	6	5	5	5	5					
10 ⁻⁴	26			5	5	5					
10 ⁻⁵	52				26	7					
10 ⁻⁶											
10 ⁻⁷											
10 ⁻⁸											



Note: the content of darkened cells was not determined respectively is unnecessary Rev - No: 1 Creation date of this sheet: 15.10.2013

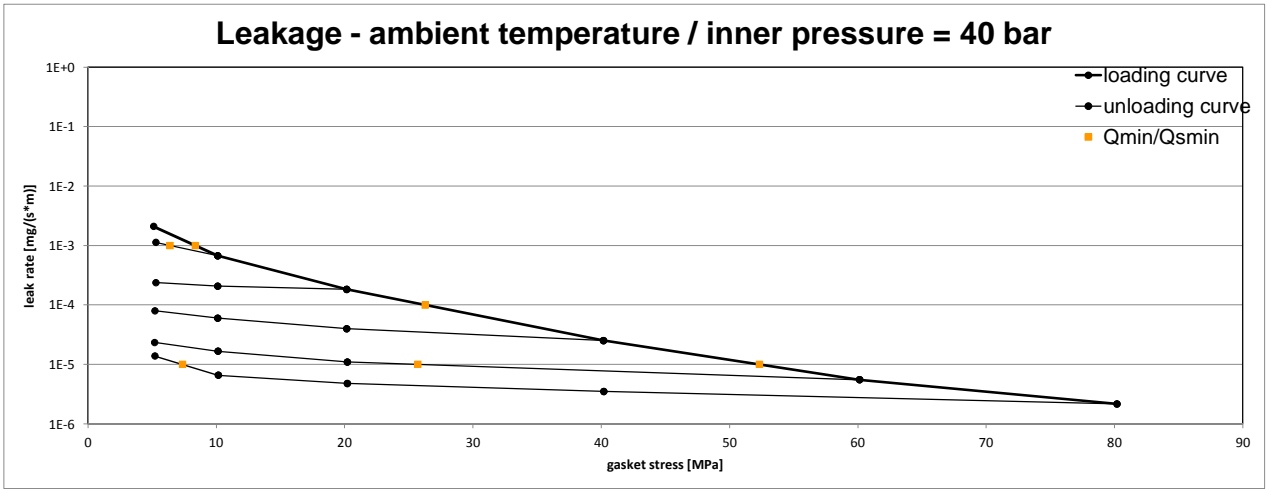