



Company Address	W. L. Gore & Associates GmbH, Hermann-Oberth-Strasse 22, 85640 Putzbrunn, Germany	According to DIN EN 13555 2014-07
Gasket Type	GORE® STA-PURE® Pipe Gasket Style 1500	
Sealing element dimensions [mm]	92 x 49 x 1.5	

L [mg/(s*m)]	Q _{minL} [MPa]	Minimum stress to seal Q _{minL} (at assembly), Q _{SminL} (after off-loading) for p = 10 bar									
		Q _{SminL} [MPa]									
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa				
10 ⁰	5	5	5	5	5	5	5				
10 ⁻¹	5	5	5	5	5	5	5				
10 ⁻²	5	5	5	5	5	5	5				
10 ⁻³	5	5	5	5	5	5	5				
10 ⁻⁴	30				7	5	5				
10 ⁻⁵	45					5	5				

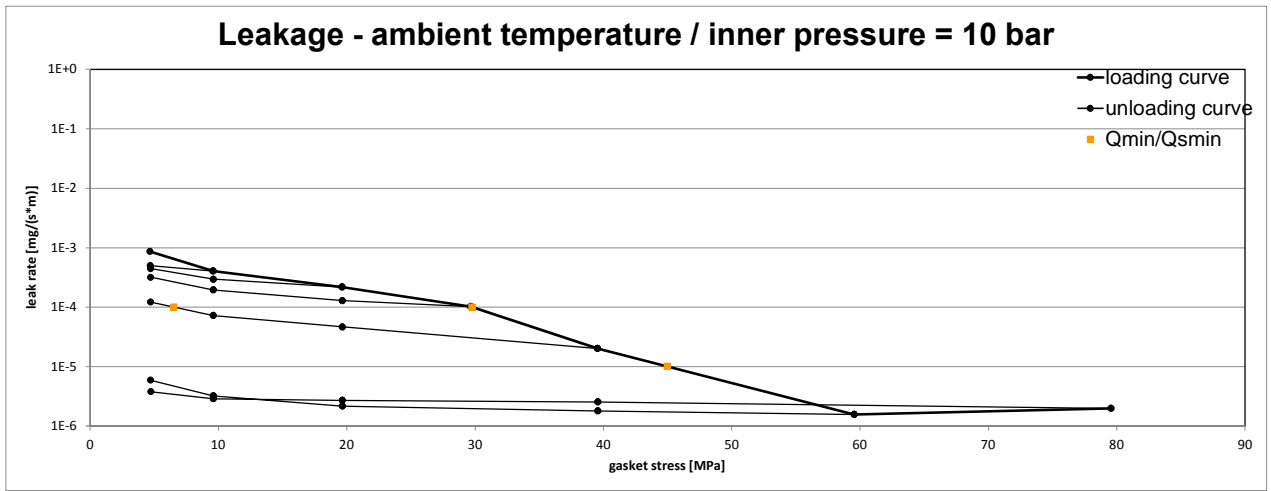


L [mg/(s*m)]	Q _{minL} [MPa]	Minimum stress to seal Q _{minL} (at assembly), Q _{SminL} (after off-loading) for p = 20 bar									
		Q _{SminL} [MPa]									
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa				
10 ⁰	5	5	5	5	5	5	5				
10 ⁻¹	5	5	5	5	5	5	5				
10 ⁻²	5	5	5	5	5	5	5				
10 ⁻³	8	7	7	5	5	5	5				
10 ⁻⁴	34				14	5	5				
10 ⁻⁵	50					6	5				

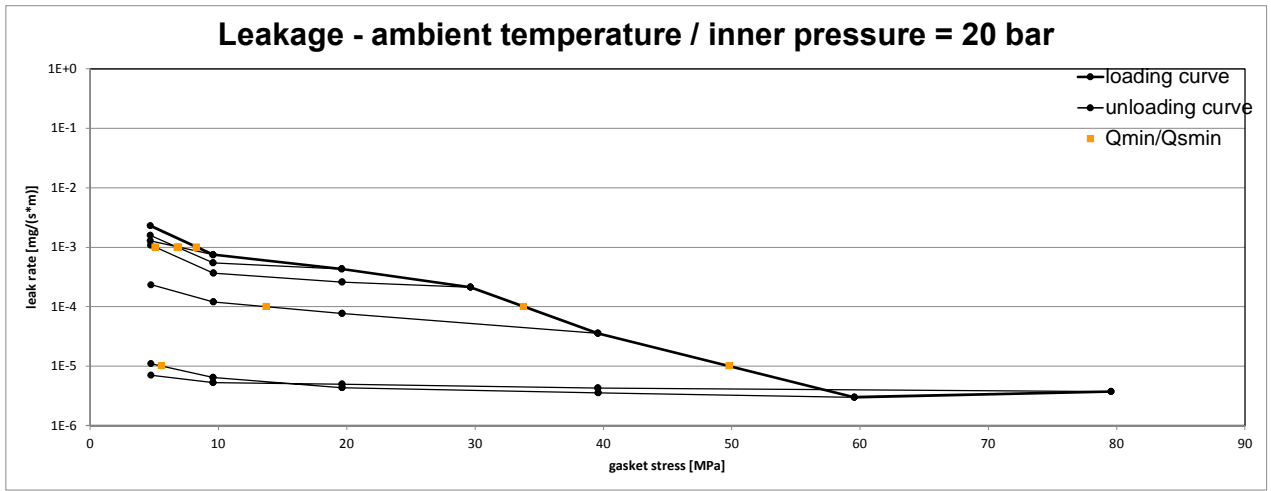

Note: the content of darkened cells was not determined respectively is unnecessary Rev - No: 1 Creation date of this sheet: 2016-01-25

Company Address	W. L. Gore & Associates GmbH, Hermann-Oberth-Strasse 22, 85640 Putzbrunn, Germany	According to DIN EN 13555 2014-07
Gasket Type	GORE® STA-PURE® Pipe Gasket Style 1500	
Sealing element dimensions [mm]	92 x 49 x 1.5	

L [mg/(s*m)]	Q _{min,L} [MPa]	Minimum stress to seal Q _{min,L} (at assembly), Q _{Smin,L} (after off-loading) for p = 40 bar							
		Q _{Smin,L} [MPa]							
		Q _A = 10 MPa	Q _A = 20 MPa	Q _A = 30 MPa	Q _A = 40 MPa	Q _A = 60 MPa	Q _A = 80 MPa		
10 ⁰	5	5	5	5	5	5	5		
10 ⁻¹	6	5	5	5	5	5	5		
10 ⁻²	8	5	5	5	5	5	5		
10 ⁻³	22			14	5	5	5		
10 ⁻⁴	40					5	5		
10 ⁻⁵	56					16	7		

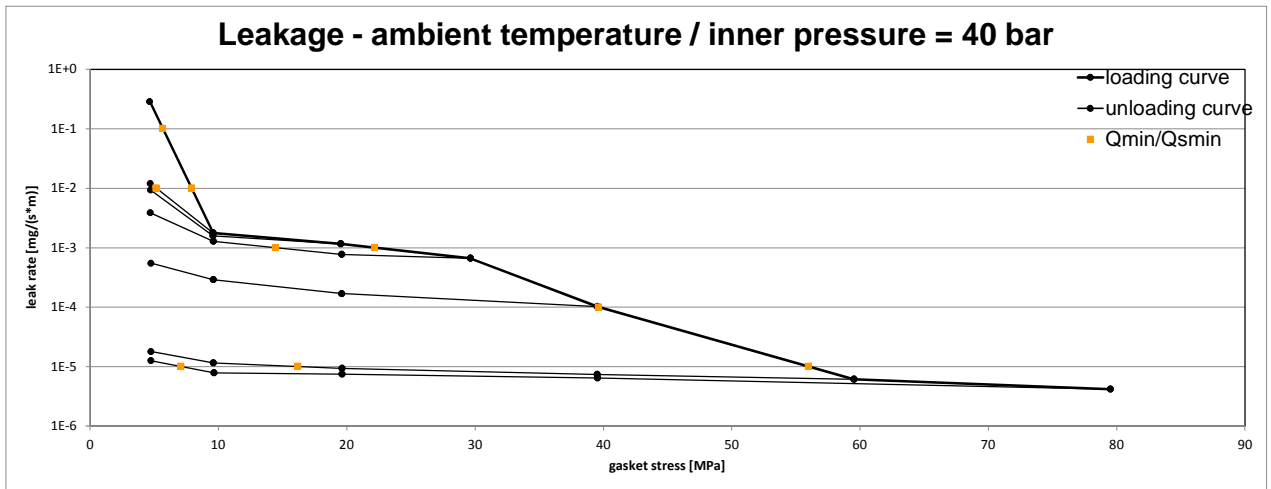

Note: the content of darkened cells was not determined respectively is unnecessary Rev - No: 1 Creation date of this sheet: 2016-01-25

